Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

TEST REPORT

Austex Commercial Fabrics Client:

PO Box 15

Thomastown VIC 3074

Test Number :

19-005960

Issue Date Print Date

30/10/2019 30/10/2019

"Studio" **Sample Description** Clients Ref:

> Embossed leather look textile coated onto knitted scrim 85% PVC, 15% Polyester Nominal Composition: 700g/m2 Nominal Mass per Unit Area/Density:

Approx: 1mm Nominal Thickness:

AS/NZS 3837-1998 Method of Test for Heat and Smoke Release Rates for Materials and Products using an Oxygen

Consumption Calorimeter

30/10/2019 **Date Tested**

AWTA Test Operator 2 Operator

Face Tested Face

		- P								
	1	2	3	4	5	6	Mean			
Average Heat Release Rate	38.6	26.0	46.0	43.3	30.1	31.2	35.9	kW/m²		
Average Specific extinction area	283.1	383.5	233.9	242.4	333.4	322.2	299.7	m²/kg		

(according to Specification C1.10 of the Building Code of Australia)

Specimen

Test orientation: Horizontal

	Specimen						
1	2	3	4	5	6	Mean	
50	50	50	50	50	50	50	kW/m²
0.024	0.024	0.024	0.024	0.024	0.024	0.024	m³/s
9	6	6	6	8	8	7	sec
300	301	305	320	290	300	303	sec
159.0	154.4	144.8	174.5	128.6	140.4	150.3	kW/m²
73.8	81.0	98.9	107.3	89.8	93.3	90.7	kW/m²
	0.024 9 300 159.0	50 50 0.024 0.024 9 6 300 301 159.0 154.4	1 2 3 50 50 50 0.024 0.024 0.024 9 6 6 300 301 305 159.0 154.4 144.8	1 2 3 4 50 50 50 50 0.024 0.024 0.024 0.024 9 6 6 6 300 301 305 320 159.0 154.4 144.8 174.5	1 2 3 4 5 50 50 50 50 50 0.024 0.024 0.024 0.024 0.024 9 6 6 6 8 300 301 305 320 290 159.0 154.4 144.8 174.5 128.6	1 2 3 4 5 6 50 50 50 50 50 0.024 0.024 0.024 0.024 0.024 0.024 9 6 6 6 8 8 300 301 305 320 290 300 159.0 154.4 144.8 174.5 128.6 140.4	1 2 3 4 5 6 Mean 50 50 50 50 50 50 0.024 0.024 0.024 0.024 0.024 0.024 0.024 9 6 6 6 8 8 7 300 301 305 320 290 300 303 159.0 154.4 144.8 174.5 128.6 140.4 150.3

115546 39750 Page 1 of 14

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved



Accredited for compliance with ISO/IEC 17025 - Testing

- Chemical Testing

- Mechanical Testing - Performance & Approvals Testing

Accreditation No Accreditation No. : Accreditation No 983

985

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA



Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.

APPROVED SIGNATORY

ANAGING DIRECTOR

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

TEST REPORT

Client: Austex Commercial Fabrics

PO Box 15

Thomastown VIC 3074

Test Number :

19-005960

Issue Date

30/10/2019

int Date	:	30/10/2019	

Average heat at 180 s	50.8	34.4	64.2	60.5	40.8	42.1	48.8	kW/m²
Average heat at 300 s	n/a	n/a	n/a	n/a	n/a	n/a	n/a	kW/m²
Total heat released	11.2	7.7	13.7	13.6	8.4	9.1	10.6	MJ/m²
Ave. effective heat of combustion	6.2	4.4	7.4	6.7	4.5	5.1	5.7	MJ/kg
Initial thickness	7.5	7	7	7	7	7	7.1	mm
Initial mass	91.5	91.5	92.4	92.9	100.1	96.4	94.1	g
Mass at sustained flaming	91.5	91.2	92.4	92.6	100.1	95.9	94.0	g
Mass remaining	76.8	77.4	77.2	76.5	84.7	82.0	79.1	g
Mass percentage pyrolysed	16.0	15.4	16.4	17.7	15.4	14.9	16.0	%
Mass loss	1.8	1.7	1.9	2.0	1.9	1.8	1.9	kg/m²
Average rate of mass loss	6.2	5.9	6.2	6.5	6.7	6.1	6.3	g/m².s

Additional Observations

None

Difficulties Encountered during Testing

None

These test results relate only to the behaviour of the product under the conditions of the test, they are not intended to be the sole criterion for assessment of performance under real fire conditions.

The results of these fire tests may be used to directly assess fire hazard, but it should be recognised that a single test method will not provide a full assessment of the fire hazard under all fire conditions.

Samples were adhered to a substrate of 6mm thick cement sheet using Professional Ultra Clear Pro 880 adhesive prior to testing

Tests were conducted with a wire grid placed over the sample during testing . This was done to contain intumescing sample within the sample holder.

115546

39750

Page 2 of 14

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved



Accredited for compliance with ISO/IEC 17025 - Testing

- Chemical Testing

- Mechanical Testing

- Performance & Approvals Testing

: Accreditation No. 983 : Accreditation No. 985 : Accreditation No. 1356

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.





MICHAEL A. JACKSON B.Sc.(I

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

TEST REPORT

Austex Commercial Fabrics Client:

PO Box 15

Thomastown VIC 3074

19-005960 Test Number :


30/10/2019 **Issue Date**

Print Date 30/10/2019


Specimen:

Heat release rate (kW/m²) 200 160 120 80 40 40 120 160 200 240 280 320 Time (s)


Effective heat of combustion (MJ/kg)

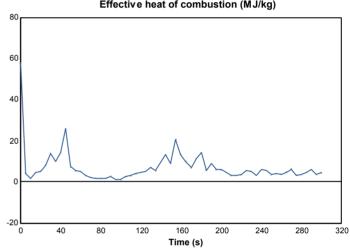

Smoke production rate ([m²/s])

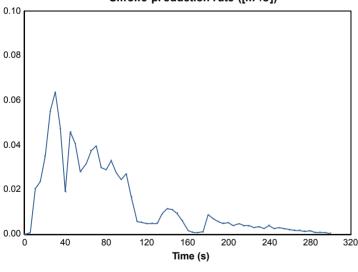

Specific extinction area (m²/kg)

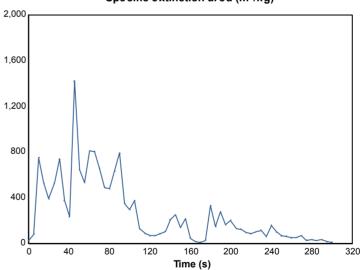

115546

39750

Page 3 of 14

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved



Accredited for compliance with ISO/IEC 17025 - Testing

- Chemical Testing

 Mechanical Testing Performance & Approvals Testing Accreditation No Accreditation No.

985

Accreditation No

983



Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.



Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

TEST REPORT

Client: Austex Commercial Fabrics


PO Box 15


Thomastown VIC 3074


Test Number : 19-005960


Issue Date : 30/10/2019

Print Date : 30/10/2019

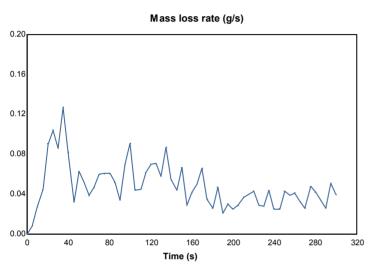

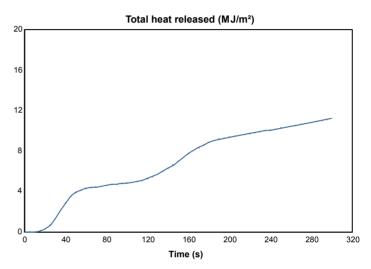

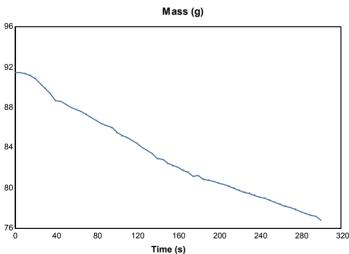

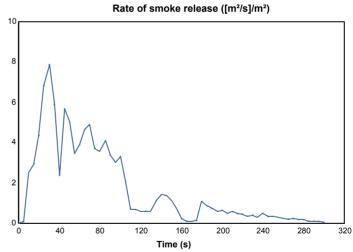

115546 39750 Page 4 of 14

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved

NATA

Accredited for compliance with ISO/IEC 17025 - Testing

- Chemical Testing

- Mechanical Testing

Performance & Approvals Testing

: Accreditation No. 983 : Accreditation No. 985 : Accreditation No. 1356

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.



MICHAEL A. JACKSON B.Sc.(Hons

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

TEST REPORT

Austex Commercial Fabrics Client:

PO Box 15

Thomastown VIC 3074

19-005960 Test Number :

Issue Date


Print Date 30/10/2019

30/10/2019


2 Specimen:

Heat release rate (kW/m²) 200 160 120 80 40 40 120 160 200 240 280 320 Time (s)


Effective heat of combustion (MJ/kg)

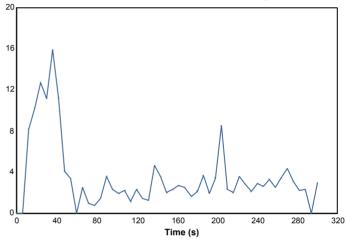

Smoke production rate ([m²/s])

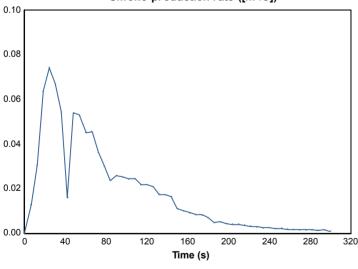

Specific extinction area (m²/kg)

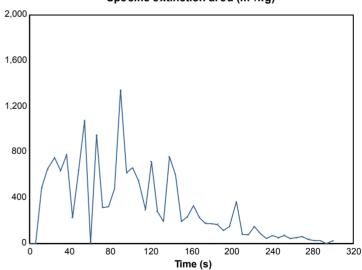

115546

39750

Page 5 of 14

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved



Accredited for compliance with ISO/IEC 17025 - Testing

- Chemical Testing

Mechanical Testing

Performance & Approvals Testing

Accreditation No 983 Accreditation No. 985 Accreditation No 1356

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.



ANAGING DIRECTOR

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

TEST REPORT

Austex Commercial Fabrics Client:


PO Box 15


Thomastown VIC 3074


19-005960 Test Number :


Issue Date 30/10/2019

30/10/2019 **Print Date**

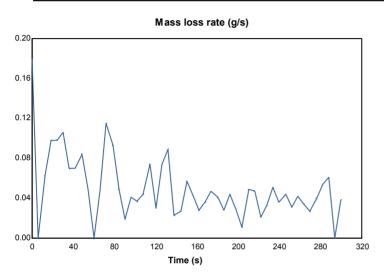

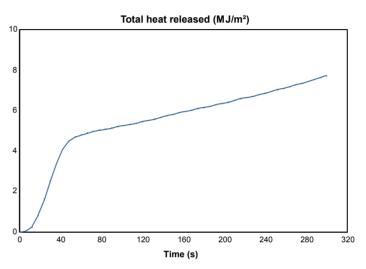

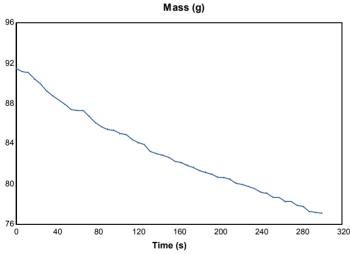

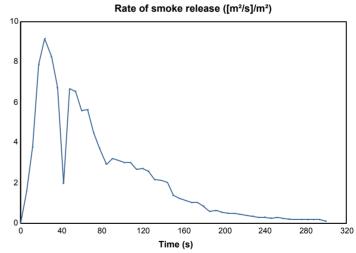

115546 39750 Page 6 of 14

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved

Accredited for compliance with ISO/IEC 17025 - Testing

- Chemical Testing

Mechanical Testing

Performance & Approvals Testing

Accreditation No 983 Accreditation No. 985 Accreditation No

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.



ANAGING DIRECTOR

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing
A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

TEST REPORT

Client: Austex Commercial Fabrics

PO Box 15

Thomastown VIC 3074

Test Number : 1
Issue Date : 3


19-005960


Print Date

30/10/2019 30/10/2019


Specimen: 3

Heat release rate (kW/m²) 160 120 80 40 40 80 120 160 160 200 240 280 320 Time (s)

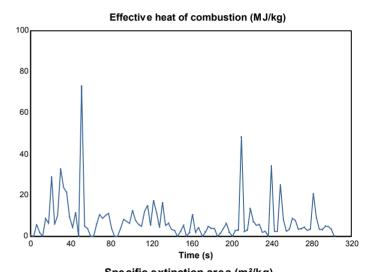

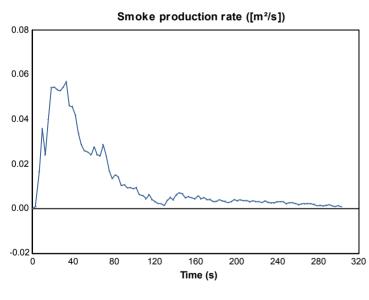

39750

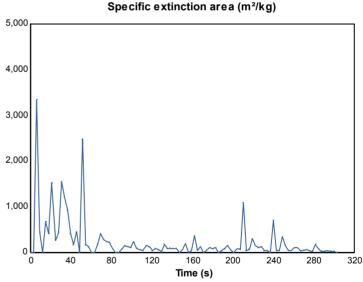

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved

115546

Accredited for compliance with ISO/IEC 17025 - Testing

- Chemical Testing

- Mechanical Testing - Performance & Approvals Testing : Accreditation No. 983 : Accreditation No. 985 : Accreditation No. 1356

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.

AWTA LIMITED

Page 7 of 14

APPROVED SIGNATORY

MICHAEL A. JACKSON B.Sc.(Hons)

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

TEST REPORT

Austex Commercial Fabrics Client:

PO Box 15

Thomastown VIC 3074

19-005960 Test Number :

Issue Date 30/10/2019 30/10/2019 **Print Date**

Mass loss rate (g/s) 0.20 0.15 0.10 0.0 0.00 40 80 120 200 240 280 0 160 320 Time (s)

Total heat released (MJ/m²) 20 16 12 40 80 120 160 200 240 280 320 Time (s)

Mass (g) 92 88 84 80 280 40 80 120 160 200 240 320 Time (s)

Rate of smoke release ([m²/s]/m²) 120 160 200 40 80 240 280 320 Time (s)

115546 39750 Page 8 of 14

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved

Accredited for compliance with ISO/IEC 17025 - Testing

- Chemical Testing

Mechanical Testing

Performance & Approvals Testing

Accreditation No 983 Accreditation No. 985 Accreditation No

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.



ANAGING DIRECTOR

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

TEST REPORT

Client: Austex Commercial Fabrics

PO Box 15

Thomastown VIC 3074

Test Number : 1 Issue Date : 3

19-005960 30/10/2019

Print Date


30/10/2019


Specimen: 4

Heat release rate (kW/m²) 160 120 80 40 50 100 150 200 250 300 350 Time (s)

Effective heat of combustion (MJ/kg) 50 40 20 10

Time (s)

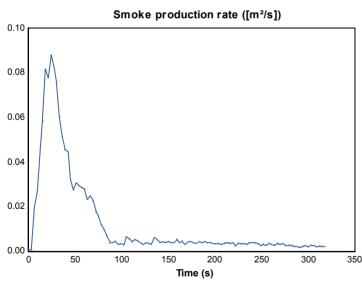

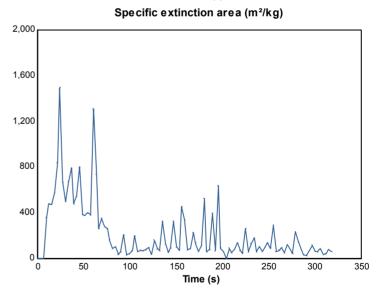

115546

39750

Page 9 of 14

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved



Accredited for compliance with ISO/IEC 17025 - Testing

- Chemical Testing

- Mechanical Testing

Performance & Approvals Testing

: Accreditation No. 983 : Accreditation No. 985 : Accreditation No. 1356

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.



350

MICHAEL A. JACKSON B.Sc.(Ho

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

TEST REPORT

Austex Commercial Fabrics Client:

PO Box 15


Thomastown VIC 3074


Test Number : Issue Date


19-005960


30/10/2019

30/10/2019 **Print Date**

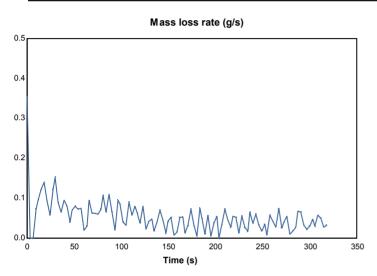

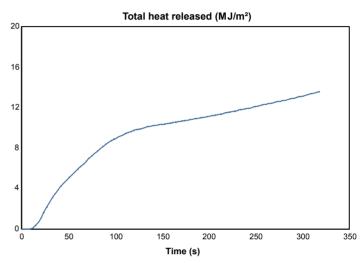

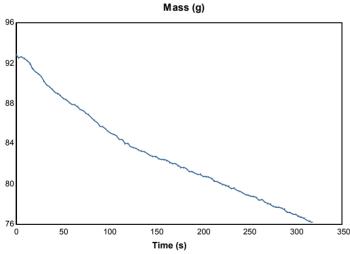

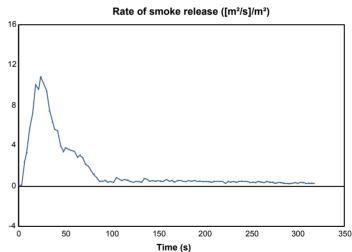

115546

39750

Page 10 of 14

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved

Accredited for compliance with ISO/IEC 17025 - Testing

- Chemical Testing

Mechanical Testing

Performance & Approvals Testing

Accreditation No 983 Accreditation No. 985 Accreditation No

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.



ANAGING DIRECTOR

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

TEST REPORT

Austex Commercial Fabrics Client:

PO Box 15

Thomastown VIC 3074

19-005960 Test Number :


30/10/2019 **Issue Date**

Print Date 30/10/2019


5 Specimen:

Heat release rate (kW/m²) 200 160 120 80 40 40 160 200 240 280 320 Time (s)


Effective heat of combustion (MJ/kg)

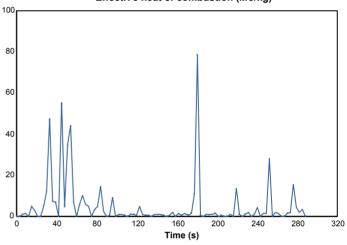

Smoke production rate ([m²/s])

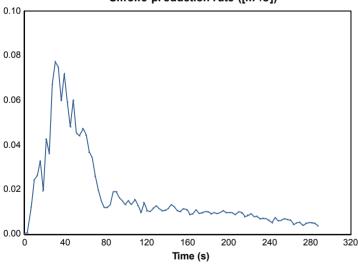

Specific extinction area (m²/kg)

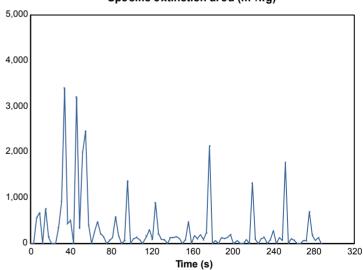

115546

39750

Page 11 of 14

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved



Accredited for compliance with ISO/IEC 17025 - Testing

- Chemical Testing

Mechanical Testing

Performance & Approvals Testing

Accreditation No 983 Accreditation No. 985 Accreditation No

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.



ANAGING DIRECTOR

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

TEST REPORT

Client: Austex Commercial Fabrics


PO Box 15


Thomastown VIC 3074


Test Number : 19-005960


Issue Date : 30/10/2019

Print Date : 30/10/2019

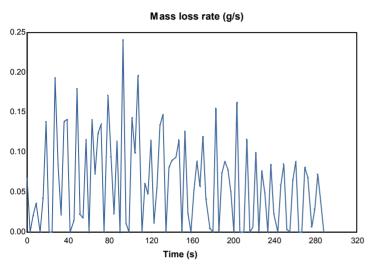

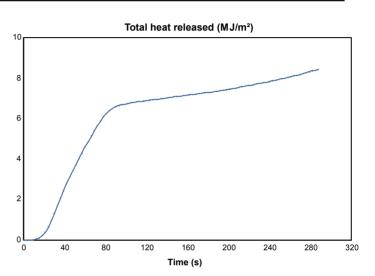

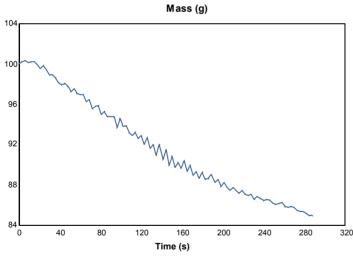

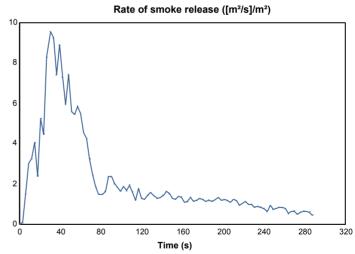

115546 39750

Page 12 of 14

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved



Accredited for compliance with ISO/IEC 17025 - Testing

- Chemical Testing

- Mechanical Testing

Performance & Approvals Testing

: Accreditation No. 983 : Accreditation No. 985 : Accreditation No. 1356

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.



MICHAEL A. JACKSON B.Sc.(Hons

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

TEST REPORT

Austex Commercial Fabrics Client:

PO Box 15

Thomastown VIC 3074

Test Number :

19-005960 30/10/2019


Issue Date Print Date

30/10/2019


Specimen:

Heat release rate (kW/m²) 200 160 120 80 40 40 160 200 240 280 320 Time (s)


Effective heat of combustion (MJ/kg)

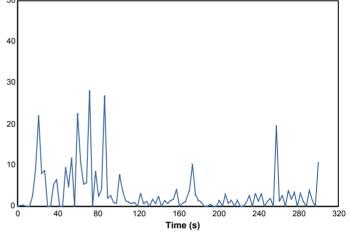

Smoke production rate ([m²/s])

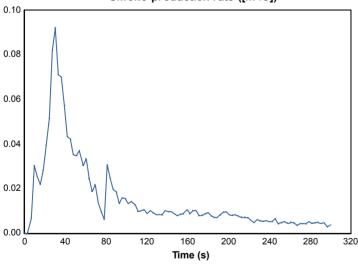

Specific extinction area (m²/kg)

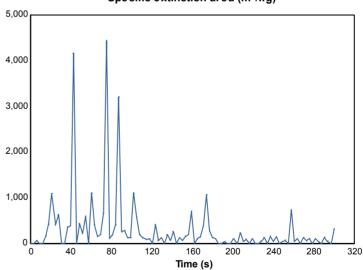

115546

39750

Page 13 of 14

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved



Accredited for compliance with ISO/IEC 17025 - Testing

- Chemical Testing

 Mechanical Testing Performance & Approvals Testing Accreditation No.

985

Accreditation No Accreditation No 983

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.

APPROVED SIGNATORY

ANAGING DIRECTOR

Australian Wool Testing Authority Ltd - trading as AWTA Product Testing A.B.N 43 006 014 106

1st Floor, 191 Racecourse Road, Flemington, Victoria 3031 P.O Box 240, North Melbourne, Victoria 3051 Phone (03) 9371 2400 Fax (03) 9371 2499

TEST REPORT

Client: Austex Commercial Fabrics


PO Box 15


Thomastown VIC 3074


Test Number : 19-005960


Issue Date : 30/10/2019

Print Date : 30/10/2019

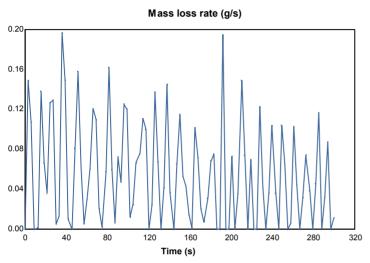

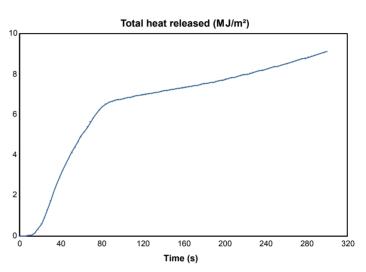

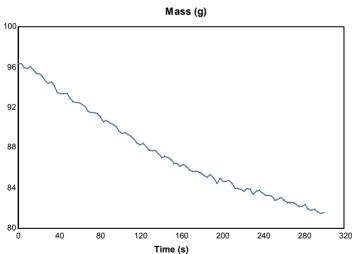

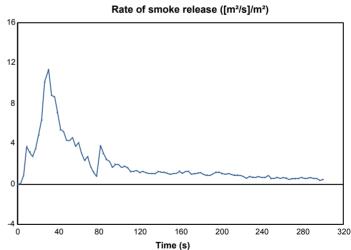

115546 39750

Australian Wool Testing Authority Ltd Copyright - All Rights Reserved NATA

Accredited for compliance with ISO/IEC 17025 - Testing

- Chemical Testing

Performance & Approvals Testing

: Accreditation No. 983 : Accreditation No. 985 : Accreditation No. 1356

Samples and their identifying descriptions have been provided by the client unless otherwise stated. AWTA Ltd makes no warranty, implied or otherwise, as to the source of the tested samples. The above test results relate only to the sample or samples tested. This document shall not be reproduced except in full and shall be rendered void if amended or altered. This document, the names AWTA Product Testing and AWTA Ltd may be used in advertising providing the content and format of the advertisement have been approved by the Managing Director of AWTA Ltd.



Page 14 of 14

MICHAEL A. JACKSON B.Sc.(Hons)