

## Technical data sheet and product guideline



# RU5BLACK-X

### Extra black ruthenium for bath plating 5g/l

#### Color coordinates



#### Product form

Metal concentration	<b>5 g/l (Ru)</b>
Form	<b>Liquid</b>
Material color	<b>Black</b>
Storage time	<b>2 years</b>
Format	<b>Ready to use</b>
Chemical type	<b>Acidic</b>
Volume	<b>1 liter</b>

#### Operating data

	Range	Optimal
Voltage (V)	<b>2,0-5,0</b>	<b>3,5</b>
Current density (A/dm <sup>2</sup> )	<b>3-5</b>	<b>3,5</b>
Working temperature (°C)	<b>65-70</b>	<b>65</b>
Exposure time (sec)	<b>300-900</b>	<b>420-600</b>
pH	<b>0.8-1.2</b>	<b>1.2</b>
Cathode efficiency (mg/Amin)	<b>1-3</b>	<b>2</b>
Anode/cathode ratio	<b>2:1-4:1</b>	<b>3:1</b>
Anode type	<b>Platonized titanium</b>	
Agitation	<b>Strong</b>	

#### Metal concentration

Metal	Range (g/l)	Optimal (g/l)
Ruthenium	<b>3-10</b>	<b>5</b>

#### Deposit data

Purity (%)	<b>99.9</b>
Hardness (HV 0,01)	<b>600-800</b>
Density (g/cm <sup>3</sup> )	<b>10.5</b>
Appearance	<b>Shiny</b>
Color	<b>Black</b>

## Preparation

RU5BLACK-X is a ready-to-use galvanic bath at the concentration of 5 g/l. No preparation is required.

## Equipment

Working vessel: Pyrex glass / PVC / polypropylene.

Power supply: DC current rectifier with low residual AC (<5%).

Heating element.


Anode Type Platinized Titanium [1.5-2.5 µm].

For larger bath volumes:

Magnetic driven filter pumps with 5-15 µm cartridge (before use, boil and wash the cartridges with demineralized water for 3 hours to prevent organic contamination).

Amp/min counter.

## Pre treatment

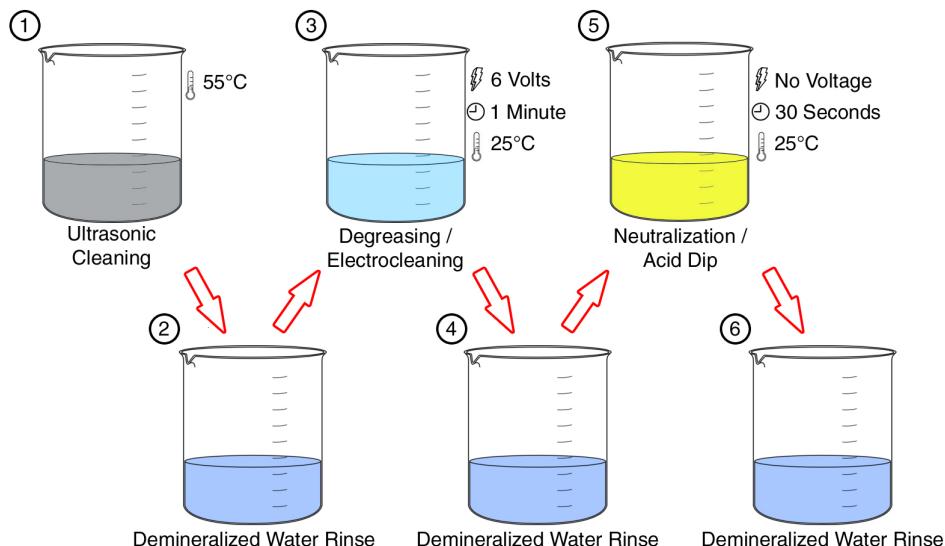

## Bath maintenance

### Metallic additions

For small-size ruthenium baths (up to 3 liters) we advise to use until the rhodium solution is completely exhausted and dispose without incorporating replenishment. For larger-sized baths add **RU5R** which is a pre calibrated replenisher containing additional ruthenium in concentrate to restore the optimal ruthenium concentration. For perfect galvanic bath performance it is advisable to maintain the rhodium concentration at a minimum of 20% of the initial concentration; for example, with a bath operating at a concentration of 5 g/l, additions should be made after a maximum consumption of 1 g/l of rhodium. When introducing additional metal bare in mind that in optimum working conditions a bath working at 5 g/l normally deposits about 3 mg of ruthenium per Ampere/minute.

### pH control

pH is a very important parameter especially when working on high thickness layers. The pH value must be frequently controlled and held under optimal values numerically described in the operating data table.

In the case corrections are needed use Ammonium hydroxide to raise the pH, and **RU5S** conductive salts to lower it.

### Density control

Solution density is not a critical parameter. In the case of heavy productions, it is advised to control the density periodically by chemical titration. As the density lowers in value, restore to its optimum working health using **RU5S** conductive salts. Adding 10 g/l of **RU5S** will raise the solution density of about 1° Bé.

## Post treatment

The electrolyte should be removed from the surface as quick as possible.

1. Wash off the bath residual in a recovery rinse (still rinse) followed by
2. Wash the article in hot distilled water (80°C).
3. Rinse the parts in circulating or running water.
4. Dry

In the case a problem is observed, replace step #2 with a 50% cold ammonia solution rinse for 5 minutes. This action should be performed under an exhaust hood.

## Water purity

To prevent contamination of the bath both during its preparation and any subsequent replenishing operations, use demineralized water with a conductivity of less than 3 µS/cm (containing no traces of organic compounds, Chlorine, Silicon, or Boron).

## Safety information

Being an acidic solution, the electrolyte is corrosive therefore is an irritant to the skin, eyes and mucous membranes. Caution should be exercised when using the product, avoiding contact with the eyes and skin. Use gloves and safety goggles. Keep away from cyanide based chemicals. For further information please refer to the relative MSDS.

## Packaging



LEGOR GROUP S.p.A. - Via del Lavoro, 1 - 36050 Bressanvido (VI) Italy - tel. +39 0444 467911 - fax +39 0444 660677 - info@legor.com - www.legorgroup.com