

## ***Additional reaction to fire classification report Nr 13854A***

### **Owner of the classification report**

BN INTERNATIONAL B.V.  
Rokerijweg 5  
NL-1271 AH HUIZEN  
THE NETHERLANDS

### **Introduction**

This classification report defines the classification assigned to the product '**Digifort P300**' in accordance with the procedures given in the standard EN 13501-1: 2007: Fire classification of construction products and building elements - Part 1: classification using data from reaction to fire tests.

**This classification report consists of 5 pages**

## 1. DETAILS OF CLASSIFIED PRODUCT

### a) Nature and end use application

The product "**Digifort P300**" is defined as a 'decorative wall covering'.  
Its classification is valid for the following end use application(s):  
'Used for attaching onto walls or ceilings, by means of an adhesive'

### b) Description

The product "**Digifort P300**" consists of a vinyl based wall covering with a paper backing. The weight of the vinyl layer (PVC) is 210 g/m<sup>2</sup>. The weight of the paper backing is 90g/m<sup>2</sup>.

	Nominal value
Mass per unit area (g/m <sup>2</sup> )	300

Mounting: The product was glued onto a calcium silicate board (12,5mm, 870 kg/m<sup>3</sup>) with BK10-PVA adhesive (200g/m<sup>2</sup>).

## 2. TEST REPORTS AND TEST RESULTS IN SUPPORT OF THIS CLASSIFICATION

### a) Test reports

Name of the laboratory	Name of the sponsor	Test report ref. Nr.	Test method
WFRGENT N.V. Ghent, Belgium	BN International B.V.	9634, 12700D, 12700E	EN 13823 (February 2002)
WFRGENT N.V. Ghent, Belgium	BN International B.V.	12700A, 12700B, 12700C	EN ISO 11925-2 (February 2002)
WFRGENT N.V. Ghent, Belgium	BN International B.V.	12700G	EXAP according to CEN/TS 15117

b) Test results

Test method	Parameter	Number of tests	Results		Criteria for Class B-s2,d0	
			Continuous parameters Mean	Compliance parameters	Continuous parameters	Compliance parameters
EN ISO 11925-2 (*) (1) 30s flame application: <u>Surface exposure</u> - front side	$F_s \leq 150\text{mm}$ Ignition filter paper	6	(-) (-)	Yes No	(-) (-)	Yes No
	<u>Edge exposure</u> - front side	$F_s \leq 150\text{mm}$ Ignition filter paper	6	(-) (-)	Yes No	(-) (-)
EN 13823 (2)	FIGRA <sub>0,2 MJ</sub> (W/s)	3	95	(-)	$\leq 120$	(-)
	FIGRA <sub>0,4 MJ</sub> (W/s)		(-)	(-)	(-)	
	LFS <sub>&lt;edge</sub>		(-)	Yes	(-)	Yes
	THR <sub>600s</sub> (MJ)		1,5	(-)	$\leq 7,5$	(-)
	SMOGRA (m <sup>2</sup> /s <sup>2</sup> )		18	(-)	$\leq 180$	(-)
	TSP <sub>600s</sub> (m <sup>2</sup> )		67	(-)	$\leq 200$	(-)
	Flaming droplets/particles f<10s		(-)	Yes	(-)	Yes
	f>10s		(-)	No	(-)	No
EN ISO 11925-2 (*) (3) 30s flame application: <u>Surface exposure</u> - front side	$F_s \leq 150\text{mm}$ Ignition filter paper	6	(-) (-)	Yes No	(-) (-)	Yes No
	<u>Edge exposure</u> - front side	$F_s \leq 150\text{mm}$ Ignition filter paper	6	(-) (-)	Yes No	(-) (-)
EN 13823 (4)	FIGRA <sub>0,2 MJ</sub> (W/s)	3	18	(-)	$\leq 120$	(-)
	FIGRA <sub>0,4 MJ</sub> (W/s)		(-)	(-)	(-)	
	LFS <sub>&lt;edge</sub>		(-)	Yes	(-)	Yes
	THR <sub>600s</sub> (MJ)		1,8	(-)	$\leq 7,5$	(-)
	SMOGRA (m <sup>2</sup> /s <sup>2</sup> )		7	(-)	$\leq 180$	(-)
	TSP <sub>600s</sub> (m <sup>2</sup> )		55	(-)	$\leq 200$	(-)
	Flaming droplets/particles f<10s		(-)	Yes	(-)	Yes
	f>10s		(-)	No	(-)	No

(-) Not applicable

(\*) The material did not melt nor pull away from the pilot burner.

(1) Based on the results obtained in test report Nr. 12700A, "Digifort P300" white, design 2013

(2) Based on the results obtained in test report Nr. 9634, "Digifort P300" white, design 2013

(3) Based on the results obtained in test report Nr. 12700B, "Digifort P300" black, design 2193

(4) Based on the results obtained in test report Nr. 12700D, "Digifort P300" black, design 2193

EN ISO 11925-2 (*) (5) 30s flame application: <u>Edge exposure</u> - front side	$F_s \leq 150\text{mm}$ Ignition filter paper	6	(-) (-)	Yes No	(-) (-)	Yes No
EN 13823 (6)	FIGRA <sub>0,2 MJ</sub> (W/s) FIGRA <sub>0,4 MJ</sub> (W/s) LFS <sub>-edge</sub> THR <sub>600s</sub> (MJ) SMOGRA (m <sup>2</sup> /s <sup>2</sup> ) TSP <sub>600s</sub> (m <sup>2</sup> ) Flaming droplets/particles f<10s f>10s	2	15 (-) (-) 1,7 8 56 (-) (-)	(-) (-) Yes (-) (-) (-) Yes No	$\leq 120$ (-) (-) $\leq 7,5$ $\leq 180$ $\leq 200$ (-) (-)	(-) (-) Yes (-) (-) (-) Yes No

(-) Not applicable

(\*) The material did not melt nor pull away from the pilot burner.

(5) Based on the results obtained in test report Nr. 12700C, "Digifort P300" red, design 2423

(6) Based on the results obtained in test report Nr. 12700E, "Digifort P300" red, design 2423

### 3. CLASSIFICATION AND DIRECT FIELD OF APPLICATION

#### a) Reference and direct field of application

This classification has been carried out in accordance with clause 10.6 of EN 13501-1: 2007 and prEN 15102: 2004.

#### b) Classification

The product "**Digifort P300**" in relation to its reaction to fire behavior is classified as:

Fire behavior	Smoke production	Flaming droplets
<b>B</b>	<b>s2</b>	<b>d0</b>

#### c) Field of application

This classification for the product as described in §1b, is valid for the following end use conditions :

- Glued on any backing with a fire performance of A2 or better with a density of equal to or greater than 870 kg/m<sup>3</sup> and a thickness of equal to or greater than 11 mm.
- Without a void
- Fixing: glued with BK10-PVA adhesive (200g/m<sup>2</sup>)
- With joints

This classification is valid for the following product parameters:

- Nominal mass per unit area: 300 g/m<sup>2</sup>
- All colours

#### 4. RESTRICTIONS

At the time the standard EN 13501-1 (2007) was published, no decision was made concerning the duration of validity of a classification report.

#### 5. WARNING


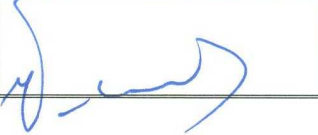
This classification report does not represent type approval nor certification of the product.

The following statement is included in accordance with Fire Sector Group Recommendation 001:

“The classification assigned to the product in this report is appropriate to a declaration of conformity by the manufacturer within the context of a system 3 attestation of conformity and CE marking under the Construction Products Directive.

The manufacturer has made a declaration, which is held on file. This confirms that the product's design requires no specific processes, procedures or stages (e.g. no addition of flame-retardants, limitation of organic content, or addition of fillers) that are aimed at enhancing the fire performance in order to obtain the classification achieved. As a consequence the manufacturer has concluded that system 3 attestation is appropriate.

The test laboratory has, therefore, played no part in sampling the product for the test, although it holds appropriate references to the manufacturer's factory production control that is aimed to be relevant to the samples tested and that will provide for their traceability.”

Report	Name	Signature (*)	Date
Prepared by	Ing. Frans DUTRIEUE		24 MAART 2009
Reviewed by	Prof. Dr. Ir. Paul VANDELDE		24 MAART 2009
(*) For and on behalf of "WFRGENT N.V."			

EN 13501-1 B-C-D WG 3E\*

The present report constitutes an addition to Test Report Nr 12700F dated 12/06/2007. It has been drafted in accordance with the regulations of EGOLF regulation R4 "Application Note : clause 5.10 [5.10/4] – Issue 01 - 2001/03/12 – amendment of test reports : clients changing product / company names (II) – for commercial reasons". The product "Digifort P300" has not been retested. Present additional report does not contain any technical modifications to the original test report. Both the original and the new denomination of the product and of the company entrusted with marketing the product will be documented and entered in the laboratory's archives.

This report may be used only literally and completely for publications. - For publications of certain texts, in which this report is mentioned, our permission must be obtained in advance.