



Infrastructure Technologies

Gate 5, 2 Normanby Road Clayton VIC 3168, Australia

Telephone: 61 3 9545 2777 Web: <http://www.csiro.au>

Registered Testing Authority - CSIRO

8 October 2018

Our Ref. EN13 / 2469 03/0212

TEST REPORT No. 8160

Requested by: Armstrong Flooring Pty Ltd
29-39 Mills Road
Braeside
VIC 3195
on (date): 25 September 2018
Manufacturer: Armstrong Flooring
Product Desc.: Austalis Vinyl Flooring

Sampling details:

Where: Delivered
Date: 25 September 2018
By whom: Courier
How (methods): N/A

The results reported relate only to the sample(s) tested and the information received. No responsibility is taken for the accuracy of the sampling unless it is done under our own supervision. CSIRO cannot accept responsibility for deviations in the manufactured quality and performance of the product. While CSIRO takes care in preparing the reports it provides to clients, it does not warrant that the information in this particular report will be free of errors or omissions or that it will be suitable for the client's purposes. CSIRO will not be responsible for the results of any actions taken by the client or any other person on the basis of the information contained in the report or any opinions expressed in it. The reproduction of this test report is only authorised in the form of a complete photographic facsimile. Our written approval is necessary for any partial reproduction.

This test report consists of 4 pages

SUMMARY OF SLIP RESISTANCE TESTS PERFORMED:

		Result	Class
AS 4586:2013	Slip resistance classification of new pedestrian surface materials Appendix A: WET PENDULUM TEST METHOD (Slider 96): Mean SRV:	42	P3

In order to interpret the classifications, please refer to Standards Australia Handbook 198, An Introductory Guide to the Slip Resistance of Pedestrian Surface Materials, which recommends minimum classifications for a wide variety of locations.

It is important to realise that test results obtained on unused factory-fresh samples may not be directly applicable in service, where proprietary surface coatings, contamination, wear and subsequent cleaning all influence the behaviour of the pedestrian surface.



Infrastructure Technologies


Gate 5, 2 Normanby Road Clayton VIC 3168, Australia

Telephone: 61 3 9545 2777 Web: <http://www.csiro.au>

REPORT NO: 8160
ISSUE DATE: 8 October 2018
MANUFACTURER: Armstrong Flooring
PRODUCT DESC: Austalis Vinyl Flooring

Page 2 of 4

PHOTOS:

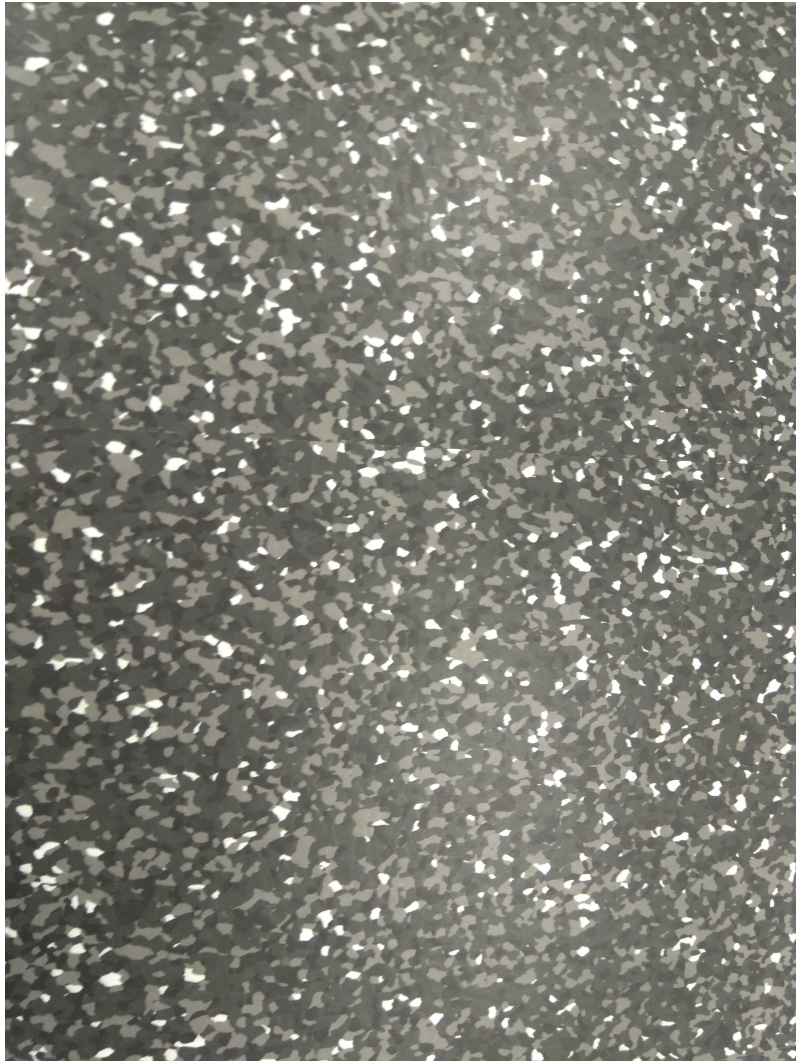



REPORT NO: 8160
ISSUE DATE: 8 October 2018
MANUFACTURER: Armstrong Flooring
PRODUCT DESC: Austalis Vinyl Flooring

SLIP RESISTANCE CLASSIFICATION OF NEW PEDESTRIAN SURFACE MATERIALS

WET PENDULUM TEST METHOD

TEST CARRIED OUT IN ACCORDANCE WITH
AS 4586:2013 (Appendix A)

Test Date: 8 October 2018

RESULTS:	Location:	Slip Resistance Laboratory	Slider used: 96
	Sample:	Unfixed	Conditioned with grade P400 paper, dry
	Cleaning:	Deionized water	and Imperial Lapping Film Grade 3MIC, wet
	Temperature:	22°C	

Pendulum Friction Tester: ERM 030.040 (S/N: 1726, calibrated 06/09/18)
Test conducted by: Andy Giang

	Specimen				
	1	2	3	4	5
Last 3 swings (BPN)	41	44	42	39	45
	41	44	42	40	45
	41	44	42	40	45
Averages	41	44	42	40	45

Mean SRV : 42

CLASS :

P3

Where products are to be used in wet barefoot areas, it is more appropriate to test to Appendix C of AS 4586 (which is technically equivalent to DIN 51097).



Infrastructure Technologies

Gate 5, 2 Normanby Road Clayton VIC 3168, Australia

Telephone: 61 3 9545 2777 Web: <http://www.csiro.au>

REPORT NO: 8160
ISSUE DATE: 8 October 2018
MANUFACTURER: Armstrong Flooring
PRODUCT DESC: Austalis Vinyl Flooring

Page 4 of 4

Date and Place 8 October 2018, Clayton, Vic

Name, Title and Signature:

A large, light gray watermark of the CSIRO logo is centered on the page. It consists of the stylized bar chart icon above the word "CSIRO" in a large, bold, sans-serif font.

ANDY GIANG
Technical Officer
Tel: 61 3 95452777
Email: Andy.Giang@csiro.au