

RECIPE - 30CL

LAVENDER SPA IN RS1

CANDLE

DESCRIPTION



INGREDIENTS FOR EACH CANDLE

1x 30cl glass jar
22.0g of Lavender Spa Fragrance Oil
198.0g of Candle Shack Ecosystem RS1 Wax
1x CL18 Wick
1x 15mm Adhesive Wick Pad
1x WickClaw Tool for 30cl Glass

WAX

Candle Shack's EcoSystem RS1 Wax is a natural wax blend made from rapeseed and soy oils. Developed exclusively for Candle Shack, this professional-grade wax is easy to use by novice and seasoned chandler alike and is particularly popular with our luxury clients. This plant wax is also easy to wick and offers good scent throw with compatible fragrances.

VESSEL

Our Lotti 30cl glass is manufactured in Italy and meets the highest standards of clarity and tolerance.

Height: 90mm
Diameter: 78mm
Internal height: 75mm

WICK

Our innovative unbleached cotton and linen blend CL Series wick. Flat wick designed to minimise afterglow and smoking while maintaining rigidity. All wicks are 110mm long with a thin paraffin wax coating for stability.

USAGE RECOMMENDATIONS

- We recommend heating RS1 to a maximum of 75°C (slowly to prevent damaging the wax).
- Add fragrance at 63°C and stir for 60 seconds.
- The mixture is ready to pour at 60°C into warmed glasses.
- If the top is uneven once set, you can flash the surface with a heat gun, or do a top up pour to get a clean finish.
- Leave the candle to cure for 2+ days for best results.

DISCLAIMER

Each report shows test results for a set of candles made by Candle Shack's R&D team for that particular recipe. The test reports are not a guarantee that all candles made to the recipe will burn in exactly the same way. Variables such as ambient temperature, air flow, or the manufacturing process can affect the burning profile of a candle, so it is recommended that candle makers conduct their own testing to ensure that they are satisfied with the performance of their product.



Candle Shack Ltd Unit A, West Carron Works Stenhouse Rd Carron Stirlingshire FK2 8DR

Technical report on a test set of candles made in Candle Shack R&D department for sooting behaviour testing and fire safety testing

Date of Report: 23/09/21 Testing Period: 22/08/2021 - 30/08/2021

Sample Ref	CS0299A-1	No. of Samples	3		
Candle Name	30cl lavender Spa Candle, 10% in RS1				
Description	220g Rapeseed Container Blend Wax Fragranced Candle				
Fragrance	Lavender Spa		Weight per candle	22.0g	
Wax	Candle Shack Ecosystem RS1		Weight per candle	198.0g	
Colour	White	Height	92mm		
Wick Type	CL18	Top Diameter (ext)	82mm		
Wick Positioning	Centred	Top Diameter (int)	76mm		
Surface Defects	None	Base Diameter	76mm		

TECHNICAL REPORT

Part 1: SPECIFICATION FOR SOOTING BEHAVIOUR

To evaluate the performance of a test set of candles in a controlled environment against the requirements of **BS EN 15426:2018** (Candles. Specification for sooting behaviour)

Part 2: SPECIFICATION FOR FIRE SAFETY

To evaluate the performance of a test set of candles in a controlled environment against the requirements of **BS EN 15493:2019** (Candles. Specification for fire safety)

Page 1 of 5



Candle Shack Ltd Unit A, West Carron Works Stenhouse Rd Carron Stirlingshire FK2 8DR

Part 1: SPECIFICATION FOR SOOTING BEHAVIOUR

Requirement

When tested in accordance with clause 9 of EN 15426:2018, the average soot index per hour from three tests (samples) shall be less than 1.0/h

The room temperature during testing was 20±5°C

Wicks were trimmed to 5mm before lighting.

Cycles: 3 x 240 ± 5 min cycles with >60min pause between cycles)

Soot testing was performed in wire mesh cylinder Type 2 (Diameter: 300 ± 10 mm)

	Sample Ref.	Total burn time t_m (h)	Hourly soot index Si _h	Average soot index per hour Si _h	Result
Γ	CS0299A-1	12.67	0.11	8	
Γ	CS0299A-2	12.67	0.14	0.10	PASS
Γ	CS0299A-3	12.67	0.05	3	

Page 2 of 5

CANDLE SHACK

Candle Shack Ltd Unit A, West Carron Works Stenhouse Rd Carron Stirlingshire FK2 8DR

Part 2: SPECIFICATION FOR FIRE SAFETY

Test Property	Test Method	Requirements	Result	
I STADILITY I		Candle should not tip over when placed on a 10° incline plane	PASS	
Secondary Ignition	EN 15493:2019 4.2 (Visual Check)	No secondary ignition shall occur for more than 10 s	PASS	
Flame Height	EN 15493:2019 4.3 (Measurement)	The flame height for all candle types, except for tea lights, shall not exceed 75mm. The flame height for tea lights	PASS	
	,	shall not exceed 30mm	Maximum: 25 mm	
	EN 15493:2019 4.5.1 (Visual Check)	After extinguishing the candle shall not spontaneously re-light	PASS	
Behaviour after extinguishing	EN 15493:2019 4.5.2 (Measurement)	The wick shall not continue to glow or smoke for an average time of more than 30 s after extinguishing	PASS	
			Average: 6 s	
C		The container shall not crack or break at any time throughout the burning test	PASS	

The room temperature during testing was 20±5°C Wicks were trimmed to 5mm before lighting.

Candle Performance (240 ± 5 min cycles with >60min pause between cycles)

Sample Ref.	Gross Weight (g)	Total Wax	•	Wax Consumption
-	7 071	Consumed (g)	Time (h)	Rate (g/h)
CS0299A-1	538.7	211.6	52.9	4.00
CS0299A-2	528.8	197.6	48.9	4.04
CS0299A-3	545.1	198.5	52.9	3.75

^{*}If a candle self-extinguishes during the final burn cycle, the time of self-extinguishing is estimated.


Notes and Discussion:		


Page 3 of 5



Candle Shack Ltd Unit A, West Carron Works Stenhouse Rd Carron Stirlingshire FK2 8DR

CHARTS

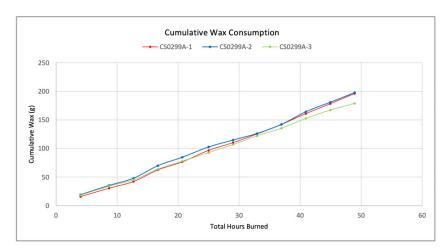

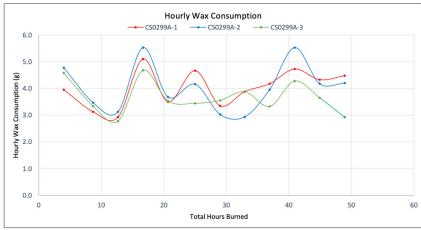

Page 4 of 5

CANDLE SHACK

Candle Shack Ltd Unit A, West Carron Works Stenhouse Rd Carron Stirlingshire FK2 8DR

IMAGE GALLERY







End of Burn Front - Sample 2



End of Burn Front - Sample 3



End of Burn Top - Sample 1



End of Burn Top - Sample 2



End of Burn Top - Sample 3

END OF REPORT

DRZam

David Barn Head of R&D