



CERTIFICATE OF TESTING

For the Account Of: Softline Home Fashions
13122 S. Normandie Ave.
Gardena, CA 90249
Contact: Candice Sta Ana

Client's Identification: Euro Linen

TEST PERFORMED California Technical Bulletin 117: June 2013 – Requirements, Test Procedure and Apparatus for Testing the Smolder Resistance of Materials Used in Upholstered Furniture – Cover Fabric Test

TEST RESULTS

Specimen	Char Length (in)	Extinguished in 45 minutes? (Y/N)
1	0.8	Y
2	0.7	Y
3	0.6	Y

NOTES

Test Conditions: 70 ±5°F, 50 ±5% Relative Humidity

ACCEPTANCE CRITERIA

A material is considered to pass or fail based on the following criteria:

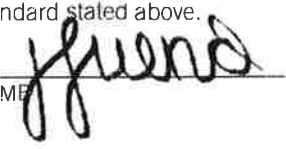
1. A single mock-up test specimen fails to meet the requirements of this test procedure if any of the following criteria occurs:
 - a. The mock-up test specimen continues to smolder after the 45 minute test duration
 - b. A vertical char length of more than 1.8 inches (45mm) develops on the cover fabric
 - c. The mock-up test specimen transitions to open flaming
2. The cover fabric passes the test if three initial mock-up specimens pass the test, i.e. the cigarettes burn their full length and are no longer smoldering
3. If more than one initial specimen fails, the cover fabric fails the test
4. If any one of the three initial specimens fails, repeat the test on additional three specimens
5. If all three additional specimens pass the test, the cover fabric passes the test. If any one of the additional three specimens fails, the cover fabric fails the test

CONCLUSION

Based on the above Results and Acceptance Criteria, the item tested is:

- Pass
 Fail

CERTIFICATION I certify that the above results were obtained after testing specimen in accordance with the procedures and equipment specified by the standard stated above.

Authorized Signature-ME 



CERTIFICATE OF TESTING

For the Account Of: Softline Home Fashions
13122 S. Normandie Ave.
Gardena, CA 90249
Contact: Candice Sta Ana

Client's Identification: Euro Linen

TEST PERFORMED NFPA 701 Standard Methods of Fire Test for Flame Propagation of Textiles and Films 2010 – Test #1

TEST RESULTS

Specimen	Initial Mass (g)	Final Mass (g)	Mass Loss (%)	Flaming Drip (s)	Afterflame (s)
1	17.5	13.6	22%	1	0
2	17.5	13.8	21%	0	0
3	17.6	13.6	23%	1	0
4	17.6	14.0	20%	1	0
5	17.5	13.7	22%	1	0
6	17.6	13.7	22%	1	0
7	17.3	13.2	24%	0	0
8	17.7	14.2	20%	0	0
9	17.5	13.8	21%	0	0
10	17.7	13.9	21%	1	0
Average	17.5	13.7	22%	0.6	0.0

Approximate weight (oz./sq. yd): 8.6

Product Configuration: Single Layer Multi Layer
 Conditioning: Oven at 220°F for minimum 30 minutes 70 ±2°F & 65 ±2%RH for minimum 24 hours
 Intended End-use (if known & other than drapery):

ACCEPTANCE CRITERIA

Afterflame is required to be recorded; however, it is not factored into the Acceptance Criteria

- Where fragments or residues of specimens that fall to the floor of the test chamber continue to burn for more than an average of 2 seconds per specimen for the sample of 10 specimens, the material shall be recorded as failing. (Flaming Drip)
- Where the average weight loss of the 10 specimens in a sample is greater than 40 percent, the material shall be recorded as failing.
- Individual specimens will be listed as a failure if it exceeds mean + 3 SD
- Where the specimens do not demonstrate performance in accordance with either of the conditions indicated above, the material shall be recorded as passing this test and shall be designated as flame resistant.

CONCLUSION

Based on the above Results and Acceptance Criteria, the item tested:
 Complies
 Does Not Comply
 Testing of 10 additional specimens is required

CERTIFICATION I certify that the above results were obtained after testing specimen in accordance with the procedures and equipment specified by the standard stated above.


Authorized Signature



CERTIFICATE OF TESTING

For the Account Of: Softline Home Fashions
13122 S. Normandie Ave.
Gardena, CA 90249
Contact: Candice Sta Ana

Client's Identification: Euro Linen

TEST PERFORMED

NFPA 260 Standard Methods of Tests and Classification System for Cigarette Ignition Resistance of Components of Upholstered Furniture – 2013; Fabric Cover Test and UFAC Fabric Classification Test Method – 1990; Standard Test Methods for Cigarette Ignition Resistance of Components of Upholstered Furniture ASTM E1353-08ae1 – Cover Fabric Test

TEST RESULTS

Specimen	Char Length (in)
1	0.8
2	0.8
3	0.7

NOTES

Test Conditions: 70 ±2°F, 65 ±2% Relative Humidity

ACCEPTANCE CRITERIA

1. If the test specimen has no ignition, or if no individual specimen yields a vertical char of 45 mm (1.75 in; ASTM states 1.8 in.) or less, the fabric is classified a Class I cover fabric.
2. If the vertical char of the test specimen greater than 45 mm (1.75 in.; ASTM states 1.8 in), the fabric is classified a Class II cover fabric.
3. If an obvious ignition of the polyurethane substrate occurs on the test assembly, the fabric is classified a Class II cover fabric.

CONCLUSION

Based on the above Results and Acceptance Criteria, the item tested is:

- Class I
- Class II

CERTIFICATION I certify that the above results were obtained after testing specimen in accordance with the procedures and equipment specified by the standard stated above.


Authorized Signature