

PRODUCT DESCRIPTION

LOCTITE® UK U-09LV is a low-viscosity, industrial grade urethane adhesive. Once mixed, the two-component urethane cures at room temperature to form an ultra-clear, highly flexible bond line, which provides excellent peel strength.

TYPICAL APPLICATIONS

Ideal for bonding polycarbonate, and a variety of other plastics, as well as glass, and metal. Suited for applications requiring a clear, non-yellowing bond line.

PROPERTIES OF UNCURED MATERIAL

Resin	Typical	
	Value	Range
Chemical Type	Polyisocyanate	
Appearance	Clear liquid	
Specific Gravity @ 25°C	1.1	1.0 to 1.2
Viscosity @ 25°C, mPa.s (cP)	920	
Flash Point (TCC), °C	See SDS	


Hardener	Typical	
	Value	Range
Chemical Type	Polyol	
Appearance	Clear Liquid	
Specific Gravity @ 25°C	1.00	0.95 to 1.15
Viscosity @ 25°C, mPa.s (cP)	1,050	600 to 2,000
Flash Point (TCC), °C	See SDS	

Mixture	Typical Value
Appearance	Ultra Clear
Specific Gravity @ 25°C	1.0 - 1.2
Mix Ratio (R:H) by Weight	100 to 91
by Volume	1 to 1

TYPICAL CURING PERFORMANCE

Cure speed

The graph below shows the shear strength developed over time on acid etched aluminum lap shears with an average bondline gap of 3 to 9 mils and tested according to STM 700.

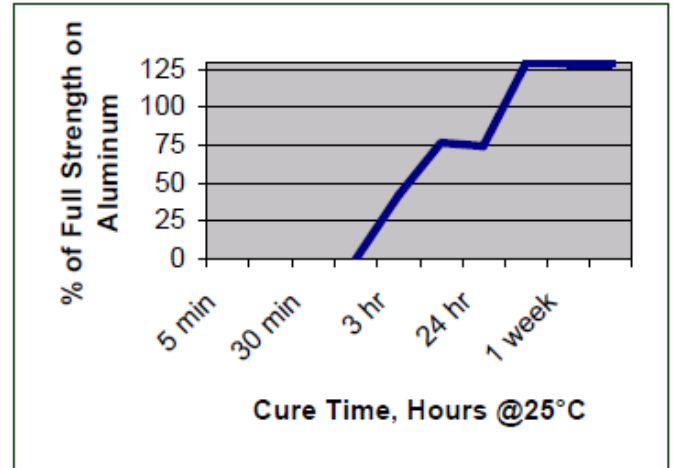

Curing Properties

(@ 25°C unless noted)	Typical Value
Working Life, minutes	10
Tack Free time, hours	3 to 24

TYPICAL PROPERTIES OF CURED MATERIAL

(@ 25°C unless noted)	Typical Value
Physical Properties	
Dielectric Strength STM 733, Volts/Mil	986
Tensile Strength STM 708, psi	2752
Tensile Elongation STM 708, %	149
Hardness STM 707, Shore D	47
Glass Transition Temperature STM 767, Tg, °C	-3
CTE pre Tg, STM 767	101ppm
CTE post Tg, STM 767	213ppm

PERFORMANCE OF CURED MATERIAL

Shear Strength vs Substrate

Substrate (Substrates cured for 5 days @ 22°C)	Typical Value	
Lapshear STM 700	N/mm ²	(psi)
Grit-Blasted Steel	8	1145
Aluminum (Acid Etched, 3 to 9 mil gap)	5.5	795
Aluminum (Anodized)	3.5	505
Stainless Steel	3.3	475
Polycarbonate	4.0	580
Nylon	1.7	240
Wood (Pine)	4.0	575


Lap Shear STM 700 (Acid Etched, 3 to 9 mil gap)	N/mm ²	(psi)
Substrate cured for 3 hrs at 65°C	2.3	335
Substrate cured for 24 hrs at 65°C	4.0	580
Substrate cured for 72 hrs at 65°C	7.1	1030
Substrate cured for 1 week at 65°C	7.6	1100

Block Shear STM 726, 5 days at RT	N/mm ²	(psi)
PVC	9.9	1430
ABS	1.8	255
Epoxy	18	2600
Acrylic	3.6	515

TYPICAL ENVIRONMENTAL RESISTANCE


Hot Strength

Test procedure : STM 700
 Substrate: Acid etched aluminum
 Bondline gap, mils: 3 to 9
 Cure procedure: 12 hours at 65°C & 4 hours at 22°C

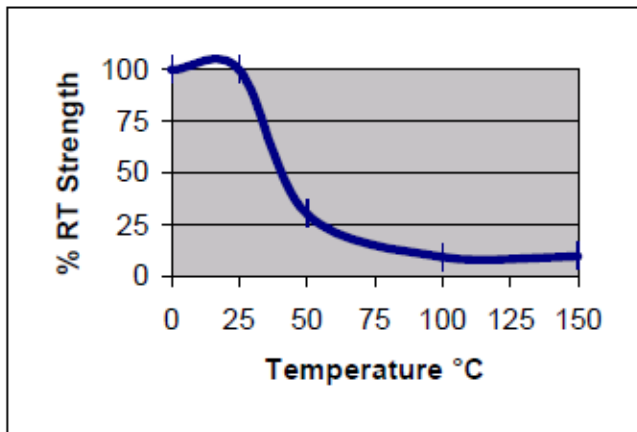

Tested at temperature.

Heat Aging

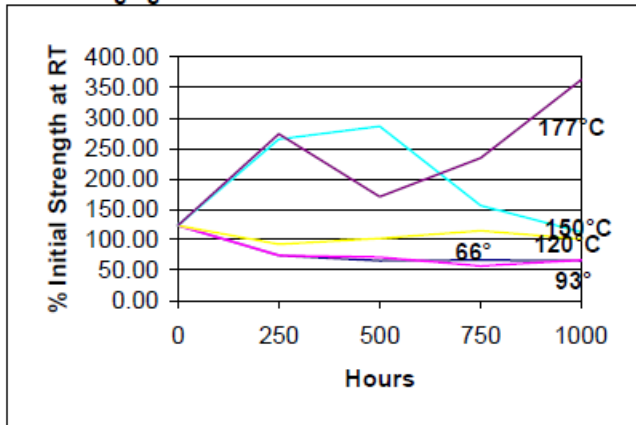

Cured for 5 days at 22°C on steel with no induced gap, aged at temperature indicated and tested at 22°C.

Chemical / Solvent Resistance

Cured for 5 days at 22°C on steel with no induced gap, aged under conditions indicated and tested at 22°C.

Solvent	Temp.	% Initial Strength retained at 500 hr	1000 hr
Air	87°C	135	140
Motor Oil (10W-30)	87°C	260	220
Unleaded Gasoline	87°C	0	0
Water/Glycol (50%/50%)	87°C	10	0
Salt/Fog ASTM B-117	22°C	0	0
95% Relative Humidity	38°C	25	30
Condensing Humidity	49°C	15	14
Water	22°C	14	21
Acetone	22°C	0	0
Isopropyl Alcohol	22°C	0	0

GENERAL INFORMATION

This product is not recommended for use in pure oxygen and/or oxygen rich systems and should not be selected as a sealant for chlorine or other strong oxidizing materials.

For safe handling information on this product, consult the Material Safety Data Sheet, (MSDS).

Directions for use

- For high strength structural bonds, removal of surface contaminants such as paint, oxide films, oils, dust, mold release agents and all other surface contaminants.
- Use gloves to minimize skin contact. DO NOT use solvents for cleaning hands.
- Dual Cartridges:** To use simply insert the cartridge into the application gun and start the plunger into the cylinders using light pressure on the trigger. Next, remove the cartridge cap and expel a small amount of adhesive to be sure both sides are flowing evenly and freely. If automatic mixing of resin and hardener is desired, attach the mixing nozzle to the end of the cartridge and begin dispensing the adhesive. For hand mixing, expel the desired amount of the adhesive and mix thoroughly. Mix approximately 15 seconds after uniform color is obtained. **Bulk Containers:** Mix thoroughly by weight or volume in the proportions specified in Properties of Uncured Material section. Mix vigorously approximately 15 seconds after uniform color is obtained.
- For maximum bond strength apply adhesive evenly to both surfaces to be joined.
- Application to the substrates should be made within 10 minutes. Larger quantities and/or higher temperatures will reduce this working time.

6. Join the adhesive coated surfaces and allow to cure at 25°C (77°F) for 24 hours for high strength. Heat up to 93°C (200°F), will speed curing.

7. Keep parts from moving during cure. Contact pressure is necessary. Maximum shear strength is obtained with a 3-9 mil bond line.

8. Excess uncured adhesive can be cleaned up with ketone type solvents.

Storage

Product shall be ideally stored in a cool, dry location in unopened containers at a temperature between 8°C to 28°C (46°F to 82°F) unless otherwise labeled. Optimal storage is at the lower half of this temperature range. To prevent contamination of unused product, do not return any material to its original container. For further specific shelf life information, contact your local Technical Service Center.

Data Ranges

The data contained herein may be reported as a typical value and/or range. Values are based on actual test data and are verified on a periodic basis.

Note

The information provided in this Technical Data Sheet (TDS) including the recommendations for use and application of the product are based on our knowledge and experience of the product as at the date of this TDS. The product can have a variety of different applications as well as differing application and working conditions in your environment that are beyond our control. Henkel is, therefore, not liable for the suitability of our product for the production processes and conditions in respect of which you use them, as well as the intended applications and results. We strongly recommend that you carry out your own prior trials to confirm such suitability of our product.

Any liability in respect of the information in the Technical Data Sheet or any other written or oral recommendation(s) regarding the concerned product is excluded, except if otherwise explicitly agreed and except in relation to death or personal injury caused by our negligence and any liability under any applicable mandatory product liability law.

In case products are delivered by Henkel Corporation, Resin Technology Group, Inc., or Henkel Canada, Inc. the following disclaimer is applicable:

The data contained herein are furnished for information only and are believed to be reliable. We cannot assume responsibility for the results obtained by others over whose methods we have no control. It is the user's responsibility to determine suitability for the user's purpose of any production methods mentioned herein and to adopt such precautions as may be advisable for the protection of property and of persons against any hazards that may be involved in the handling and use thereof. In light of the foregoing, **Henkel Corporation specifically disclaims all warranties expressed or implied, including warranties of merchantability or fitness for a particular purpose, arising from sale or use of Henkel Corporation's products. Henkel Corporation**

specifically disclaims any liability for consequential or incidental damages of any kind, including lost profits. The discussion herein of various processes or compositions is not to be interpreted as representation that they are free from domination of patents owned by others or as a license under any Henkel Corporation patents that may cover such processes or compositions. We recommend that each prospective user test his proposed application before repetitive use, using this data as a guide. This product may be covered by one or more United States or foreign patents or patent applications.

In case products are delivered by Henkel Belgium NV, Henkel Electronic Materials NV, Henkel Nederland BV, Henkel Technologies France SAS and Henkel France SA please additionally note the following:

In case Henkel would be nevertheless held liable, on whatever legal ground, Henkel's liability will in no event exceed the amount of the concerned delivery.

In case products are delivered by Henkel Colombiana, S.A.S. the following disclaimer is applicable:

The information provided in this Technical Data Sheet (TDS) including the recommendations for use and application of the product are based on our knowledge and experience of the product as at the date of this TDS. Henkel is not liable for the suitability of our product for the production processes and conditions in respect of which you use them, as well as the intended applications and results. We strongly recommend that you carry out your own prior trials to confirm such suitability of our product.

Any liability in respect of the information in the Technical Data Sheet or any other written or oral recommendation(s) regarding the concerned product is excluded, except if otherwise explicitly agreed and except in relation to death or personal injury caused by our negligence and any liability under any applicable mandatory product liability law.

Trademark usage

Except as otherwise noted, all trademarks in this document are trademarks of Henkel Corporation in the U.S. and elsewhere. ® denotes a trademark registered in the U.S. Patent and Trademark Office.